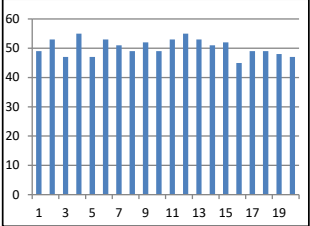
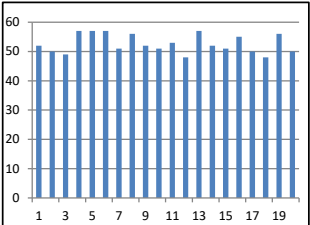
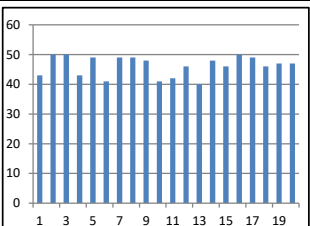
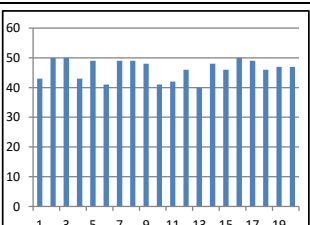
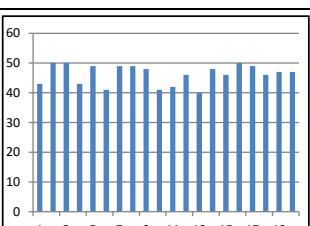


속사IC2교(진출) 반발경도시험 자료

위치	측정치	평균	타격각도	보정수치	습윤상태	수정반발도	반발경도법		재령계수	추정압축강도	비고
		R	α^0	δR	ϵR	R_0	일본재료학회	일본건축학회	α_n	F_c	
NO.1 상부구조 바닥판 하면 S1 ↑		50.4	90	-3.10	0.00	47.3	42.1	43.6	0.63	26.5 27.5 27.0	(재료학회) (건축학회) (평균)
NO.2 상부구조 바닥판 하면 S2 ↑		52.6	90	-2.86	0.00	49.7	45.1	45.4	0.63	28.4 28.6 28.5	(재료학회) (건축학회) (평균)
NO.3 하부구조 교대 구체 A1 →		46.2	0	0.00	0.00	46.2	40.7	42.9	0.63	25.6 27.0 26.3	(재료학회) (건축학회) (평균)
NO.4 하부구조 교각 구체 P1 →		45.4	0	0.00	0.00	45.4	39.7	42.3	0.63	25.0 26.6 25.8	(재료학회) (건축학회) (평균)
NO.5 하부구조 교대 구체 A2 →		45.9	0	0.00	0.00	45.9	40.3	42.6	0.63	25.4 26.8 26.1	(재료학회) (건축학회) (평균)